



Aheadd® CP1

AA8A61.50

MATERIAL DATA SHEET



MATERIAL DATA SHEET

Aheadd® CP1

AA8A61.50

MATERIAL

Aheadd® CP1 is a unique Al-alloy designed for the SLM® Process. Alloyed with minor amounts of Zr and Fe and no volatile elements such as Mg, Aheadd® CP1 has a unique combination of strength and ductility like 6000 series alloys, high thermal and electrical conductivity, an outstanding thermal stability up to 300°C, and good corrosion resistance. It can be anodized and polished to achieve the best surface properties for your application. The mechanical and thermal properties can be tailored with a single step heat treatment that does not require a quench, resulting in low anisotropy. Aheadd® CP1 is used in serial production of parts in diverse applications including heat exchangers or light weight parts under thermal load, structural parts, and crash proof parts.


CHEMICAL COMPOSITION

AA8A61.50¹

	Al	Zr	Fe
Min.	Bal.	0.9	0.8
Max.		1.4	1.4

POWDER PROPERTIES

Particle Size ¹	20-63 µm
Mass Density ²	≈ 2.73 g/cm ³
Particle Shape ^{3,4}	Spherical, typical batch morphology displayed below

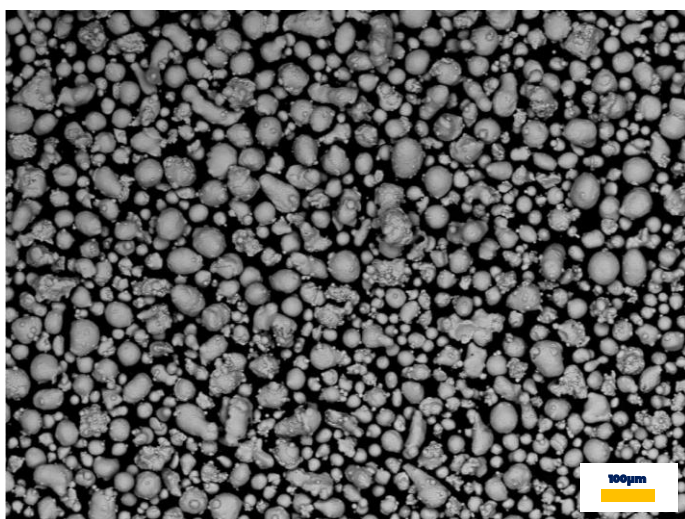

MATERIAL DATA SHEET

Aheadd® CP1


AA8A61.50

NIKON SLM® PARAMETERS

It only takes 3 tools to make you successful with metal additive manufacturing:

1. The **NIKON SLM® machine** fitting your needs,
2. The **metal powder** that defines the later purpose and functionality of a part,
3. Precisely engineered **NIKON SLM® parameters** as the missing link.

Our open parameters are the result of our vast experience in multi-laser technology and a diligent development and qualification procedure. They are key to produce fully functional parts with properties you can expect and rely on – whether you are new to AM or a large-scale production operator. We offer them to you in the following categories: **Precision (PREC)** for high-resolution complex details, **Prime (PRIM)** for balanced properties with improved productivity and **Productivity (PROD)** for the highest build rates. Pushing boundaries is in our work culture, we can also offer a new dimension of productivity on selected materials with **Productivity+ (PROD+)** and **Productivity++ (PROD++)** parameters.

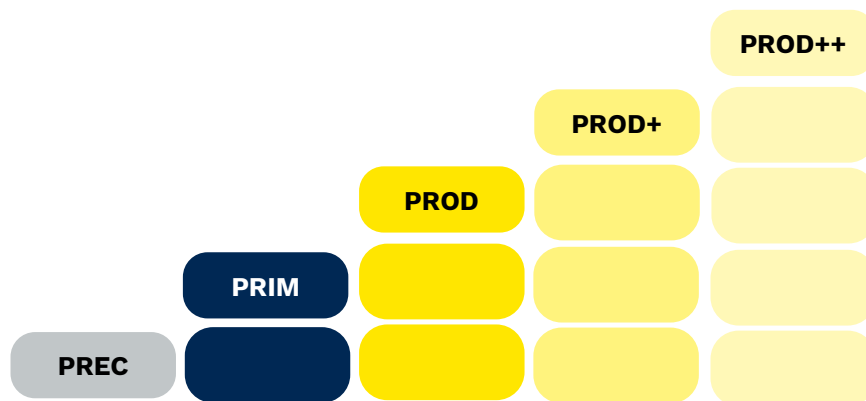

MATERIAL QUALIFICATION

As one of the inventors of the selective laser melting process, we impose the most comprehensive test procedures on ourselves: hundreds of samples, multiple systems, various powder batches, numerous heat-treatments, machined vs. near-net-shape tensile specimens, several surface roughness conditions and angles, fatigue behavior, corrosion investigation, creep testing... Did we miss anything? Get in touch with us!

MATERIAL DATA SHEET

Aheadd® CPI

AA8A61.50



SLM® 280 PRIME

Parameter Set	CP1_SLM280_PRIM_MBP3_V1 (60 µm)
Machine Compatibility	SLM® 280 2.0, SLM® 280 Production Series (700W)
Validated Data Preparation	Materialise SLM Build Processor
Theoretical System Build Rate ⁵	113.3 cm ³ /h (Twin)
Minimum Relative Density ^{6,7}	99.8 %

MECHANICAL PROPERTIES⁸

M: Mean | MIN: Minimum (95 % population coverage / 95 % confidence level)⁷

Non-heat-treated

	Tensile strength R _m [MPa]		Yield strength R _{p0.2} [MPa]		Elongation at break A [%]	
	M	MIN	M	MIN	M	MIN
Machined						
Horizontal	190	185	140	135	24	21
Vertical	190	185	130	120	24	20
Near-Net-Shape						
Vertical	180	175	125	115	29	24

Heat-treated (Aging)⁹

	Tensile strength R _m [MPa]		Yield strength R _{p0.2} [MPa]		Elongation at break A [%]	
	M	MIN	M	MIN	M	MIN
Machined						
Horizontal	305	290	270	250	18	12
Vertical	315	300	280	250	15	9
Near-Net-Shape						
Vertical	290	280	270	260	16	8

HARDNESS¹⁰

M: Mean | MIN: Minimum (95% Population Coverage / 95% Confidence Level)⁷

	Vickers hardness HV5	
	M	MIN
NHT	60	55
Aging ⁹	103	93

SURFACE ROUGHNESS¹¹

M: Mean | MAX: Maximum (95% Population Coverage / 95% Confidence Level)⁷

	Roughness average Ra [µm]		Mean roughness depth Rz [µm]	
	M	MAX	M	MAX
NHT	18	24	105	131

WALL THICKNESS

Made for Heat exchangers

Optimized border for **0.4 mm thin walls**
Capability down to **0.2 mm thin walls**
on specific geometries

Contact us for more information

CONDUCTIVITY¹²

M: Mean | MAX: Maximum (95% Population Coverage / 95% Confidence Level)⁷

	Electrical conductivity [MS/m] [%IACS]			
	M	MIN	M	MIN
NHT	17	16.8	29.4	29
Aging ⁹	27	26.7	47	46

MATERIAL DATA SHEET

Aheadd® CP1

AA8A61.50



SLM® 500 PRECISION

Parameter Set	CP1_SLM500_PREC_MBP3_V1 (30 µm)
Machine Compatibility	SLM® 500 1.3 (700 W)
Validated Data Preparation	Materialise SLM Build Processor
Theoretical System Build Rate ⁵	82.2 cm ³ /h (Quad)
Minimum Relative Density ^{6,7}	99.9 %

MECHANICAL PROPERTIES⁸

M: Mean | MIN: Minimum (95 % population coverage / 95 % confidence level)⁷

Non-heat-treated

	Tensile strength R _m [MPa]		Yield strength R _{p0.2} [MPa]		Elongation at break A [%]	
	M	MIN	M	MIN	M	MIN
Machined						
Horizontal	215	210	170	160	22	20
Vertical	210	200	160	150	22	21
Near-Net-Shape						
Vertical	200	195	145	135	27	25

Heat-treated (Aging)⁹

	Tensile strength R _m [MPa]		Yield strength R _{p0.2} [MPa]		Elongation at break A [%]	
	M	MIN	M	MIN	M	MIN
Machined						
Horizontal	340	330	300	295	13	17
Vertical	340	335	310	300	17	14
Near-Net-Shape						
Vertical	325	315	295	285	14	7

HARDNESS¹⁰

M: Mean | MIN: Minimum (95% Population Coverage / 95% Confidence Level)

	Vickers hardness HV5	
	M	MIN
NHT	68	63
Aging ⁹	107	102

SURFACE ROUGHNESS¹¹

M: Mean | MAX: Maximum (95% Population Coverage / 95% Confidence Level)

	Roughness average Ra [µm]		Mean roughness depth Rz [µm]	
	M	MAX	M	MAX
NHT	11	19	70	109

WALL THICKNESS

Made for Heat exchangers

Optimized border for **0.3 mm thin walls**
Capability down to **0.2 mm thin walls**
on specific geometries

Contact us for more information

CONDUCTIVITY¹²

M: Mean | MAX: Maximum (95% Population Coverage / 95% Confidence Level)⁷

	Electrical conductivity [MS/m]		[%IACS]	
	M	MIN	M	MIN
NHT	16.8	16.6	29	28.7
Aging ⁹	27.8	27.3	47.9	47

MATERIAL DATA SHEET

Aheadd® CP1

AA8A61.50



SLM® 500 PRIME

Parameter Set	CP1_SLM500_PRIM_MBP3_V1 (60 µm)
Machine Compatibility	SLM® 500 1.3 (700 W)
Validated Data Preparation	Materialise SLM Build Processor
Theoretical System Build Rate ⁵	226.6 cm³/h (Quad)
Minimum Relative Density ^{6,7}	99.8 %

MECHANICAL PROPERTIES⁸

M: Mean | MIN: Minimum (95 % population coverage / 95 % confidence level)⁷

Non-heat-treated

	Tensile strength R _m [MPa]		Yield strength R _{p0.2} [MPa]		Elongation at break A [%]	
	M	MIN	M	MIN	M	MIN
Machined						
Horizontal	195	185	150	140	24	21
Vertical	190	185	125	115	24	20
Near-Net-Shape	M	MIN	M	MIN	M	MIN
Vertical	185	175	130	115	29	24

Heat-treated (Aging)⁹

	Tensile strength R _m [MPa]		Yield strength R _{p0.2} [MPa]		Elongation at break A [%]	
	M	MIN	M	MIN	M	MIN
Machined						
Horizontal	305	295	270	255	17	9
Vertical	310	300	275	265	16	10
Near-Net-Shape	M	MIN	M	MIN	M	MIN
Vertical	285	275	265	260	17	12

HARDNESS¹⁰

M: Mean | MIN: Minimum (95% Population Coverage / 95% Confidence Level)

	Vickers hardness HV5	
	M	MIN
NHT	60	55
Aging ⁹	99	92

SURFACE ROUGHNESS¹¹

M: Mean | MAX: Maximum (95% Population Coverage / 95% Confidence Level)

	Roughness average Ra [µm]		Mean roughness depth Rz [µm]	
	M	MAX	M	MAX
NHT	17	23	104	133

WALL THICKNESS

Made for Heat exchangers

Optimized border for **0.4 mm thin walls**
Capability down to **0.2 mm thin walls**
on specific geometries

Contact us for more information

CONDUCTIVITY¹²

M: Mean | MAX: Maximum (95% Population Coverage / 95% Confidence Level)⁷

	Electrical conductivity [MS/m]		[%IACS]	
	M	MIN	M	MIN
NHT	17	16.6	29	28.7
Aging ⁹	28	27	48	47

MATERIAL DATA SHEET

Aheadd® CP1

AA8A61.50



SLM® 500 PRODUCTIVITY

Parameter Set	CP1_SLM500_PROD_MBP3_V1 (90 µm)
Machine Compatibility	SLM® 500 1.3 (700 W)
Validated Data Preparation	Materialise SLM Build Processor
Theoretical System Build Rate ⁵	344.8 cm³/h (Quad)
Minimum Relative Density ^{6,7}	99.0 %

MECHANICAL PROPERTIES⁸

M: Mean | MIN: Minimum (95 % population coverage / 95 % confidence level)⁷

Non-heat-treated

	Tensile strength R _m [MPa]		Yield strength R _{p0.2} [MPa]		Elongation at break A [%]	
	M	MIN	M	MIN	M	MIN
Machined						
Horizontal	185	180	120	110	24	21
Vertical	180	175	115	110	23	15
Near-Net-Shape						
Vertical	180	170	115	105	25	18

Heat-treated (Aging)⁹

	Tensile strength R _m [MPa]		Yield strength R _{p0.2} [MPa]		Elongation at break A [%]	
	M	MIN	M	MIN	M	MIN
Machined						
Horizontal	305	300	275	270	16	10
Vertical	300	290	275	265	14	7

HARDNESS¹⁰

M: Mean | MIN: Minimum (95% Population Coverage / 95% Confidence Level)⁷

	Vickers hardness HV5	
	M	MIN
NHT	56	50
Aging ⁹	98	93

SURFACE ROUGHNESS¹¹

M: Mean | MAX: Maximum (95% Population Coverage / 95% Confidence Level)⁷

	Roughness average Ra [µm]		Mean roughness depth Rz [µm]	
	M	MAX	M	MAX
NHT	14	18	85	114

MATERIAL DATA SHEET

Aheadd® CP1

AA8A61.50



NXG PRIME

Parameter Set	CP1_NXG600_PRIM_MBP3_V2 (60 µm)
Machine Compatibility	NXG XII 600 (1000 W)
Validated Data Preparation	Materialise SLM Build Processor
Theoretical System Build Rate ⁵	636 cm³/h (12 Lasers)
Minimum Relative Density ^{6,7}	99.8 %

MECHANICAL PROPERTIES⁸

M: Mean | MIN: Minimum (95 % population coverage / 95 % confidence level)⁷

Non-heat-treated

	Tensile strength R _m [MPa]		Yield strength R _{p0.2} [MPa]		Elongation at break A [%]	
	M	MIN	M	MIN	M	MIN
Machined						
Horizontal	185	180	135	130	24	22
Vertical	185	180	120	115	24	21
Near-Net-Shape	M	MIN	M	MIN	M	MIN
Vertical	180	175	120	115	28	24

Heat-treated (Aging)⁹

	Tensile strength R _m [MPa]		Yield strength R _{p0.2} [MPa]		Elongation at break A [%]	
	M	MIN	M	MIN	M	MIN
Machined						
Vertical	315	295	295	285	16	11

HARDNESS¹⁰

M: Mean | MIN: Minimum (95% Population Coverage / 95% Confidence Level)⁷

	Vickers hardness HV5	
	M	MIN
NHT	57	55
Aging ⁹	97	93

SURFACE ROUGHNESS¹¹

M: Mean | MAX: Maximum (95% Population Coverage / 95% Confidence Level)⁷

	Roughness average Ra [µm]		Mean roughness depth Rz [µm]	
	M	MAX	M	MAX
NHT	15	17	87	99

WALL THICKNESS

Made for Heat exchangers

Optimized border for **0.3 mm thin walls**
Capability down to **0.2 mm thin walls**
on specific geometries

Contact us for more information

CONDUCTIVITY¹²

M: Mean | MAX: Maximum (95% Population Coverage / 95% Confidence Level)⁷

	Electrical conductivity [MS/m]		[%IACS]	
	M	MIN	M	MIN
NHT	17	16.8	29.4	29
Aging ⁹	27	26.8	48	46

MATERIAL DATA SHEET

Aheadd® CP1

AA8A61.50



NXG PRODUCTIVITY

Parameter Set	CP1_NXG600_PROD_MBP3_V1 (90 µm)
Machine Compatibility	NXG XII 600 (1000 W)
Validated Data Preparation	Materialise SLM Build Processor
Theoretical System Build Rate ⁵	1189 cm ³ /h (12 Lasers)
Minimum Relative Density ^{6,7}	99.6 %

MECHANICAL PROPERTIES⁸

M: Mean | MIN: Minimum (95 % population coverage / 95 % confidence level)⁷

Non-heat-treated

	Tensile strength R _m [MPa]		Yield strength R _{p0.2} [MPa]		Elongation at break A [%]	
Machined	M	MIN	M	MIN	M	MIN
Vertical	190	185	120	110	23	18
Near-Net-Shape	M	MIN	M	MIN	M	MIN
Vertical	180	175	115	110	26	21

Heat-treated (Aging)⁹

	Tensile strength R _m [MPa]		Yield strength R _{p0.2} [MPa]		Elongation at break A [%]	
Machined	M	MIN	M	MIN	M	MIN
Vertical	310	295	280	270	11	4
Near-Net-Shape	M	MIN	M	MIN	M	MIN
Vertical	295	290	275	270	6	3

HARDNESS¹⁰

M: Mean | MIN: Minimum (95% Population Coverage / 95% Confidence Level)⁷

	Vickers hardness HV5	
	M	MIN
NHT	60	57
Aging ⁹	97	93

SURFACE ROUGHNESS¹¹

M: Mean | MAX: Maximum (95% Population Coverage / 95% Confidence Level)⁷

	Roughness average Ra [µm]		Mean roughness depth Rz [µm]	
	M	MAX	M	MAX
NHT	17	19	99	115

WALL THICKNESS

Made for Heat exchangers

Capability down to **0.4 mm thin walls** on specific geometries

Contact us for more information

CONDUCTIVITY¹²

M: Mean | MAX: Maximum (95% Population Coverage / 95% Confidence Level)⁷

	Electrical conductivity [MS/m]		[%IACS]	
	M	MIN	M	MIN
NHT	17	16	29	27
Aging ⁹	27	26	47	45

MATERIAL DATA SHEET

Aheadd® CPI

AA8A61.50

DISCLAIMER

The properties and mechanical characteristics apply to powder that is tested and sold by Nikon SLM Solutions, and that has been processed on Nikon SLM Solutions machines using the original Nikon SLM Solutions parameters in compliance with the applicable operating instructions (including installation conditions and maintenance). The part properties are determined based on specified procedures. More details about the procedures used by Nikon SLM Solutions are available upon request.

The specifications correspond to the most recent knowledge and experience available to us at the time of publication and do not form a sufficient basis for component design on their own. Certain properties of products or parts or the suitability of products or parts for specific applications are not guaranteed. The manufacturer of the products or parts is responsible for the qualified verification of the properties and their suitability for specific applications. The manufacturer of the products or parts is responsible for protecting any third-party proprietary rights as well as existing laws and regulations.

© 2026 Nikon SLM Solutions AG. All rights reserved. Subject to change without notice.

MDS_Aheadd® CPI_2026-6.1_EN

NOTES

¹ With respect to powder material. Compositions stated as mass or weight percent.

² Material density varies within the range of possible chemical composition variations.

³ According to DIN EN ISO 3252:2023.

⁴ Secondary Electron Image of a typical powder batch.

⁵ Theoretical system build rate = layer thickness x scan speed x hatch distance x number of lasers. The value represents a comparable indicator but remains a theoretical value after all. It does expressively not reflect true build rates, which are influenced by part geometry, ratio between hatch and contour areas, area of exposure, recoating times, and more.

⁶ Optical density determination at test specimens by light microscopy according to internal specification. Relative density may vary depending on part geometry, orientation, volume, and other process factors. Population coverage: 99%, confidence level: 99%.

⁷ Minimum values are set by using tolerance interval method, which is a statistical approach based on the input of population coverage (PC) and confidence level (CL). Tolerance intervals ensure that a certain percentage of samples within a batch will be above the minimum value with a certain probability, e.g. the probability that 95% of all samples will be above the stated minimum value (within a defined batch and tested according to mentioned specifications) is 95%.

⁸ Tensile testing was performed in accordance with DIN EN ISO 6892-1:2020 A or DIN EN ISO 6892-1:2020 B at room temperature. Samples are either machined before testing or tested in near-net-shape without any surface finishing (geometry according to DIN 50125:2022-C6x30). Samples labelled "Horizontal" correspond to a polar angle of $\theta = 90^\circ$; samples labelled "vertical" correspond to a polar angle of $\theta = 0^\circ$ (DIN EN ISO/ASTM 52921). Values include overlap samples, i.e. multiple lasers work simultaneously on one specimen. All data is derived from standardized Nikon SLM Solutions qualification jobs. Samples are built out of both virgin powder as well as used powder. Population coverage: 95 %, confidence level: 95 %. Material can be sensitive to strain rate during a tensile test.

⁹ Heat treatment aging, set temperature of 400 °C with a ramp up rate of 10 °C/min, in air, load samples or component when oven has reached 200 °C, hold at 400 °C for 4 hours, furnace cool by turning furnace off, remove samples at 200 °C or lower and air cool.

¹⁰ Hardness testing according to DIN EN ISO 6507-1:2024. Measurement direction "2" according to VDI 3405 2.1. Values include overlap samples, i.e. multiple lasers work simultaneously on one specimen. All data is derived from standardized SLM Solutions qualification jobs. Samples are built out of both virgin powder as well as used powder.

¹¹ Roughness measurement on vertical walls according to DIN EN ISO 21920-3:2022; $\lambda_c = 2.5$ mm. Values include overlap samples, i.e. multiple lasers work simultaneously on one specimen. All data is derived from standardized SLM Solutions qualification jobs. Samples are built out of both virgin powder as well as used powder.

¹² Electrical Conductivity according to DIN EN 2004-1 & ASTM E 1004. Samples are always measured on a polished cross-section.

CONTACT

Headquarters

Nikon SLM Solutions AG
Estlandring 4
23560 Lübeck
Germany

Phone: +49 451 4060-3000

www.nikon-slm-solutions.com

